



中国认可
国际互认
检测
TESTING
CNAS L6478



TEST REPORT

Reference No. : WTF20F11088926F
Applicant : Mid Ocean Brands B.V.
Address : 7/F., Kings Tower, 111 King Lam Street, Cheung Sha Wan, Kowloon,
Hong Kong
Manufacturer : 100381
Sample Name : Wicker picnic basket
Model No. : MO6193, MO6194
Test Requested : In accordance with Council of Europe Resolution 84/500/EC
(2005/31/EC), Council of Europe Resolution CM/Res(2013)9 and
Regulation (EC) No 1935/2004.
Test Conclusion : **Pass** (Please refer to next pages for details)
Date of Receipt sample : 2020-11-23
Date of Test : 2020-11-23 to 2020-11-30
Date of Issue : 2020-11-30
Test Result : Please refer to next page (s)

Remarks:

The results shown in this test report refer only to the sample(s) tested; this test report cannot be reproduced, except in full, without prior written permission of the company. The report would be invalid without specific stamp of test institute and the signatures of compiler and approver.
If the report is not stamped with the accreditation recognized seal, it will only be used for scientific research, education, and internal quality control activities, and is not used for the purpose of issuing supporting data to the society.

Prepared By:

Waltek Testing Group (Foshan) Co., Ltd.

Address: No.13-19, 2/F., 2nd Building, Sunlink International Machinery City,
Chencun, Shunde District, Foshan, Guangdong, China

Tel:+86-757-23811398 Fax:+86-757-23811381 E-mail:info@waltek.com.cn

Compiled by:

Approved by:

Abby.Zhou

Abby.Zhou / Project Engineer

Dino Zhang

Dino.Zhang / Technical Manager

**Test Results:****1. Extractable Lead and Cadmium Content**

Test Items	Result (mg/dm ²)	LOQ (mg/dm ²)	Limit (mg/dm ²)
	No.1		
Extractable Lead	ND	0.1	0.8
Extractable Cadmium	ND	0.01	0.07

Test Items	Result (mg/L)	LOQ (mg/L)	Limit (mg/L)
	No.2		
Extractable Lead	ND	0.1	4.0
Extractable Cadmium	ND	0.01	0.3

Note:

1. Test method: With reference to BS EN 1388-1: 1996 and BS EN 1388-2: 1996, sample preparation in 4% acetic acid at 22±2°C for 24 hours, analysis was performed by ICP-OES.
2. "mg/L" = milligram per litre
3. "mg/dm²" = milligram per square decimetre
4. LOQ = Limit of quantitation
5. ND = Not Detected, less than limit of quantitation
6. The specification was quoted from 84/500/EC (2005/31/EC).

WALTEK

**2. Council of Europe Resolution CM/Res(2013)9-Specific Migration of Heavy Metal**

Test Items	1st+2nd Migration (mg/kg)		LOQ (mg/kg)	Limit (mg/kg)
	No.3	No.4		
Aluminium (Al)	ND	ND	0.2	35
Antimony (Sb)	ND	ND	0.02	0.28
Chromium (Cr)	ND	ND	0.04	1.75
Cobalt (Co)	ND	ND	0.02	0.14
Copper (Cu)	ND	ND	0.2	28
Iron (Fe)	ND	ND	0.4	280
Manganese (Mn)	ND	ND	0.2	12.6
Molybdenum (Mo)	ND	ND	0.02	0.84
Nickel (Ni)	ND	ND	0.02	0.98
Silver (Ag)	ND	ND	0.02	0.56
Tin (Sn)	ND	ND	0.2	700
Vanadium (V)	ND	ND	0.01	0.07
Zinc (Zn)	ND	ND	0.2	35
Arsenic (As)	ND	ND	0.002	0.014
Barium (Ba)	ND	ND	0.2	8.4
Beryllium (Be)	ND	ND	0.01	0.07
Cadmium (Cd)	ND	ND	0.002	0.035
Lead (Pb)	ND	ND	0.01	0.07
Lithium (Li)	ND	ND	0.01	0.336
Mercury (Hg)	ND	ND	0.002	0.021
Thallium (Tl)	ND	ND	0.0002	0.0007
Magnesium (Mg)	ND	ND	0.2	--
Titanium (Ti)	ND	ND	0.02	--



Test Items	3rd Migration (mg/kg)		LOQ (mg/kg)	Limit (mg/kg)
	No.3	No.4		
Aluminium (Al)	ND	ND	0.1	5
Antimony (Sb)	ND	ND	0.01	0.04
Chromium (Cr)	ND	ND	0.02	0.25
Cobalt (Co)	ND	ND	0.01	0.02
Copper (Cu)	ND	ND	0.1	4
Iron (Fe)	ND	ND	0.2	40
Manganese (Mn)	ND	ND	0.1	1.8
Molybdenum (Mo)	ND	ND	0.01	0.12
Nickel (Ni)	ND	ND	0.01	0.14
Silver (Ag)	ND	ND	0.01	0.08
Tin (Sn)	ND	ND	0.1	100
Vanadium (V)	ND	ND	0.005	0.01
Zinc (Zn)	ND	ND	0.1	5
Arsenic (As)	ND	ND	0.001	0.002
Barium (Ba)	ND	ND	0.1	1.2
Beryllium (Be)	ND	ND	0.005	0.01
Cadmium (Cd)	ND	ND	0.001	0.005
Lead (Pb)	ND	ND	0.005	0.01
Lithium (Li)	ND	ND	0.005	0.048
Mercury (Hg)	ND	ND	0.001	0.003
Thallium (Tl)	ND	ND	0.0001	0.0001
Magnesium (Mg)	ND	ND	0.1	--
Titanium (Ti)	ND	ND	0.01	--

Note:

1. Test Method: With reference to BS EN 13130-1: 2004, analysis was performed by ICP-OES and ICP-MS.
2. Test Condition and simulant: Sample(s) were migrated with artificial tap water at 40°C for 2 hours.
3. "mg/kg" = milligram per kilogram of foodstuff in contact with
4. LOQ = Limit of quantitation
5. ND = Not Detected or lower than limit of quantitation
6. "--" = Not regulated
7. The specification was quoted from Technical Guide on Metals and alloys used in food contact materials of Council of Europe Resolution CM/Res(2013)9.




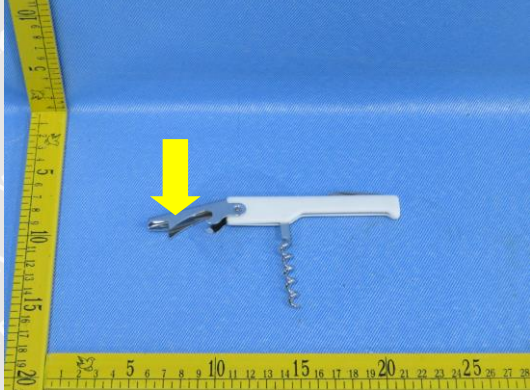


Sample Photo:





Photograph of parts tested:

No.	Photo of testing part	Parts Description	Client Claimed Material
1		White ceramic	Ceramic
2		Transparent glass	Glass
3		Silvery metal	SUS420
4		Silvery metal	Plating

==== End of Report =====